

 **AREAS OF USE**

**INDUSTRIAL**




**SUGGESTED SPECIFICATION**

**SURFACE-EMBOSSED LINEN WEAVE MIF (2.0mm)**

Supply and fix 2.0mm thick x 1.0m wide FloorworX Industrial Floor surface-embossed (linen weave) vinyl sheeting, manufactured to specification and laid in FloorworX No. 62 Acrylic adhesive spread using a TKB A2 notch trowel at a rate of between 5.5m<sup>2</sup> and 6.5m<sup>2</sup> per litre or FloorworX No. 71 contact adhesive spread using a flat trowel, brush or paint roller at a rate of approximately 3.5m<sup>2</sup> per litre (single surface application), applied to both the sheeting and the previously prepared Class 1 sub-floor as per SANS 10070 using a reliable Self-Leveller when required, including all cutting and waste. The sheeting must be rolled in both directions with an articulated 68kg three-sectional roller immediately after it has been laid into the adhesive. Joins must be butted, grooved and heat welded using FloorworX Welding Rod, ensuring that the welding rod bonds to more than 70% of the sheet thickness. The newly laid floor must, after 48 hours, be stripped using FloorworX Stripper, scrubbed using a diluted solution of FloorworX Rinse and then sealed with 3 coats of FloorworX Silk Matt or Gloss Sealer.

**SURFACE-EMBOSSED (3.5mm) / MINIDOME (3.5mm)**

Supply and fix 3.5mm thick x 1.0m wide FloorworX Industrial Floor surface-embossed / Minidome vinyl sheeting, manufactured to specification and adhered with FloorworX No. 71 contact adhesive applied to both the sheeting and the previously prepared Class 1 sub-floor in accordance with SANS 10070 (making use of a reliable Self-Leveller when required) using a brush or paint roller at the rate of approximately 3.5m<sup>2</sup> per litre per single application, including all cutting and waste. The sheeting must be rolled in both directions with an articulated 68kg three-sectional roller immediately after it has been laid into the adhesive. Joins must be butted, grooved and heat welded, using the manufacturer's welding rod, ensuring that the welding rod bonds to more than 70% of the sheet thickness. The newly laid floor must, after 48 hours, be stripped using FloorworX Stripper, scrubbed using a diluted solution of FloorworX Rinse and then sealed with three coats of FloorworX Silk Matt or Gloss Sealer.

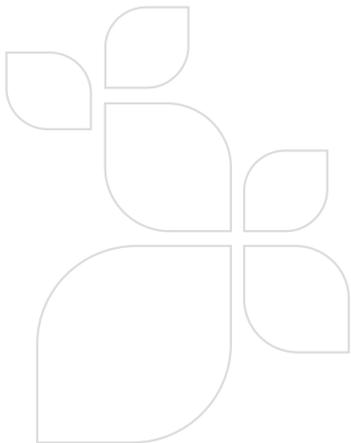

For more information please contact the **FloorworX TECHNICAL DEPARTMENT** by sending your query to [technical@floorworx.co.za](mailto:technical@floorworx.co.za)